

Oxidation of benzylic alcohols and sulfides over LaCoO_3 and TBHP

Mahesh L. Patil,^{*a,b} Suleman R. Maujan,^b Hanumant B. Borate,^b and Balu S. Uphade^b

^a*Institute of Scientific and Industrial Research (ISIR), Osaka University, Mihogaoka, Ibaraki-shi, Osaka 567-0047, Japan*

^b*National Chemical Laboratory, Dr. Homi Bhabha Road, Pune 411 008, India*
E-mail: mlpatil@rediffmail.com

Abstract

A simple and efficient methodology has been described for the selective oxidation of secondary benzylic alcohols to the corresponding ketones. In contrast, primary benzylic alcohols afforded dimethyl acetals.

Keywords: Perovskite LaCoO_3 , oxidation, benzylic alcohols, acetals

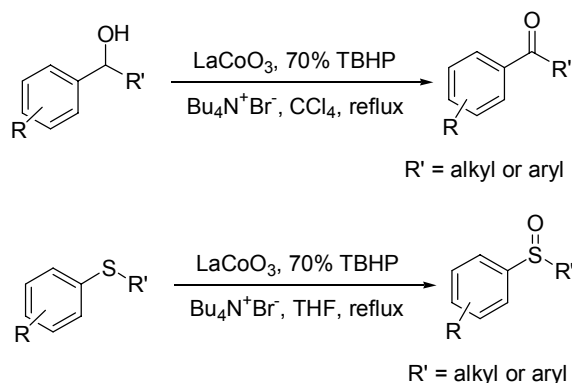
Introduction

The mineral perovskite, first described in the 1830s by the geologist Gustav Rose and named by him after the Russian mineralogist Count Lev Aleksevich von Perovski, is denoted by the chemical formula, ABO_3 wherein A is rare earth metal having +2 charge and B is transition metal such as Cr, Mn, Fe, Co, etc with +4 charge.¹ The perovskite-type oxides are non-toxic, easily handled and mild oxidizing catalysts. Despite of several advantages over traditional catalysts, they have been less explored in organic synthesis. The catalytic applications of perovskite-type oxides include hydrogenation, partial and complete oxidation of lower hydrocarbons, volatile organic compound abatement, NO reduction, fuel cells, benzylation and esterification.^{1b,2} Due to the interest in the use of environmentally friendly catalysts for organic synthesis, we undertook a study of the utility of perovskite-type oxides for the oxidation of benzylic alcohols.

The oxidation of benzylic alcohols to the corresponding carbonyl compounds is a fundamental transformation in organic synthesis.³ In spite of a number of reports employing conventional oxidizing catalysts for this transformation, the search for new catalyst is still actively pursued to address the problems like effluent pollution, loss of selectivity and tedious workup procedures.^{4,5} We envisioned the use of non-toxic perovskite type metal oxides for the oxidation of benzylic alcohols to the corresponding carbonyl compounds in the presence of oxidants.

Results and Discussion



























Among the various perovskite type metal oxides studied, LaCoO_3 was found to be very efficient catalyst for the oxidation of secondary benzylic alcohols in combination with 70% aq. TBHP (Scheme 1, table 1).⁶ The catalyst LaCoO_3 was prepared and characterized according to the known procedure.^{2b}



Scheme 1

Table 1 details the results of various secondary benzylic alcohols bearing electron withdrawing or donating groups. All substrates underwent smooth oxidation to produce corresponding ketones in excellent yields. Sterically hindered alcohols were oxidized in moderate yields (entry 5). Aromatic methyl groups were tolerated under these conditions without producing overoxidized products (entries 4 and 7). A notable feature of this methodology appeared when 4-aminobenzhydrol was subjected to oxidation under LaCoO_3 -TBHP conditions to give 4-aminobenzophenone in 90% yield (entry 8). It is noteworthy to mention that CrS-2 zeolite along with 70% aq. TBHP has been known to catalyze oxidation of alcohols^{5a} as well as amines⁷ to the corresponding ketones and nitro compounds. Development of chemoselective methodology for the selective oxidation of benzylic alcohols would be of great importance in the synthesis of fine chemicals. LaCoO_3 is a mild yet very effective catalyst for the selective oxidation of secondary benzylic alcohols. Moreover CrS-2 is more expensive and also difficult to prepare than LaCoO_3 . Additionally, LaCoO_3 -TBHP system selectively produced sulfoxides from corresponding sulfides in good to moderate yields (entries 12 and 13).

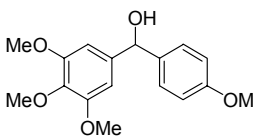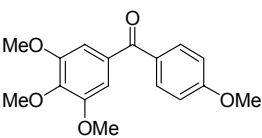
Table 1. Oxidation of benzylic alcohols and sulfides over LaCoO₃ using aq. TBHP

entry	substrate	product	time (h)	yield (%) ^b
1			6	95
2			4	84
3			10	95
4			10	92
5			10	65
6			6	95
7			10	95
8			6	90
9 ^c			24	85
10			12	75
11 ^c			14	57
12 ^c			24	48
13 ^c			24	55

^aAll reactions were carried out in CCl₄ under reflux unless otherwise mentioned. ^b Isolated yields. ^cTHF reflux

Though LaCoO_3 -aq. TBHP system holds certain advantages over known catalysts for the oxidation of secondary benzylic alcohols, it was less effective for the selective oxidation of primary benzylic alcohols. Attempts to standardize the reaction parameters for the oxidation of *m*-nitrobenzyl alcohol are summarized in table 2.

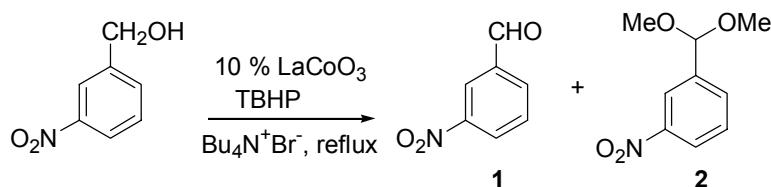Table 2. Oxidation of *m*-nitrobenzyl alcohol using LaCoO_3 -TBHP



Entry	Oxidant	Solvent	Time (h)	Product (conversion)
1 ^a	TBHP ^c	CCl_4	24	complex mixture
2 ^a	TBHP ^c	CCl_4	6	1 (15)
3 ^b	TBHP ^c	MeOH	24	1 (20), 2 (5)
4 ^b	TBHP ^d	MeOH	6	1 (30), 2 (0)
5 ^b	TBHP ^d	MeOH	24	1 (0), 2 (35)
6 ^a	TBHP ^d	CCl_4	24	1 (10)

^aDecomposition observed. ^bSignificant amounts of the starting material was recovered. ^c70% aq. TBHP was used. ^d 5-6 M TBHP in decane was used.

In contrast to secondary benzylic alcohols, the oxidation of primary benzylic alcohol using LaCoO_3 -70% aq. TBHP system in CCl_4 produced complex reaction mixture after 24 h (entry 1). Decreasing reaction time to 6 h afforded 15% of *m*-nitrobenzaldehyde (**1**) along with recovery of starting material (entry 2). Interestingly, while screening an effect of solvent, reaction in methanol yielded *m*-nitrobenzaldehyde (**1**) and *m*-nitrobenzaldehyde dimethylacetal (**2**) with conversion up to 20 and 5% respectively (entry 3). Further, the use of anhydrous TBHP (5-6 M in decane) and LaCoO_3 in MeOH after 24 h showed slight increase in the conversion of *m*-nitrobenzaldehyde to *m*-nitrobenzaldehyde dimethylacetal (**2**) (up to 35%, entry 5). However, upon reducing the time period to 6 h only *m*-nitrobenzaldehyde was obtained with conversion up to 30% (entry 4). Acetals serve as very important protecting groups in natural product synthesis. Although in present study *m*-nitrobenzaldehyde dimethylacetal (**2**) was produced in low yield, this method might provide basis for further optimization to develop a new methodology towards direct synthesis of acetals from benzyl alcohols.⁸

Exact mechanism for the LaCoO_3 -TBHP catalyzed oxidation is not known but it is believed that the lattice oxygen bound to the transition metal (cobalt) is responsible for this conversion.

In conclusion, we have demonstrated LaCoO_3 -TBHP to be a mild, effective and highly chemoselective system for the oxidation of secondary benzylic alcohols and sulfides. Although primary benzylic alcohols produced low yields of corresponding benzaldehydes, the use of

anhydrous TBHP afforded one-pot conversion of alcohols to acetals. Further studies to improve the yields of acetals are in progress.

Experimental Section

General Procedures. ^1H NMR and ^{13}C NMR spectra were recorded on a Bruker AC-200 spectrometer in CDCl_3 containing TMS as an internal standard. All solvents and reagents were purified and dried by standard procedures. TLC was carried out on silica gel plates prepared by spreading the slurry in CCl_4 and drying at room temperature. The plates were analyzed using an iodine chamber. Column chromatography was performed on silica gel (60-120 mesh). Petroleum ether refers to the fraction of boiling range 60-80 °C.

Typical experimental procedure for oxidation of alcohols to ketones (Table 1)

A mixture of benzhydrol (552 mg, 3 mmol), 70% aq. TBHP (540 mg, 6 mmol), a pinch of tetrabutylammonium bromide and LaCoO_3 (55 mg, 10% by wt) in CCl_4 (10 mL) was refluxed until completion of reaction (6 h). The catalyst was filtered off and CCl_4 layer was washed three times with saturated sodium sulfite (10 mL) to remove excess TBHP. Purification by column chromatography afforded benzophenone (518 mg, 95%).

All known compounds showed satisfactory spectral data.

Typical procedure for the conversion of *m*-nitrobenzyl alcohol to *m*-nitrobenzaldehyde dimethylacetal (2). A mixture of *m*-nitrobenzyl alcohol (153 mg, 1 mmol), TBHP (5 M solution in decane, 1 mL, 5 mmol), a pinch of tetrabutylammonium bromide and LaCoO_3 (15 mg, 10% by wt) was refluxed in anhydrous methanol for 24 h. The catalyst was filtered off followed by evaporation of solvent and purification over neutral alumina to afford *m*-nitrobenzaldehyde dimethylacetal (**2**) (70 mg, 35%). (**Caution:** Peroxides should be handled with care, although no problems were experienced in present study).

Acknowledgements

SRM thanks CSIR, New Delhi for the award of junior research fellowship. We are grateful to Dr. V. H. Deshpande (National Chemical Laboratory, Pune, India) and Prof. Dr. Hiroaki Sasai (ISIR, Osaka University, Japan) for support and encouragement.

References

1. Tejuca, L.; Fierro, J.; Tascon, J. *Adv. Catal.* **1989**, *36*, 237. (b) Seiyama, T. *Catal. Rev. Sci. Eng.* **1992**, *34*, 281. (c) Arai, H.; Yamada, T.; Eguchi, K.; Seiyama, T. *Appl. Catal.* **1986**, *26*, 265. (d) Zang, H.; Teraoka, Y.; Yamazoe, N. *Catal. Today* **1989**, *6*, 155. (e) McCarthy, J.; Wise, H. *Catal. Today* **1990**, *8*, 231. (f) Marti, G.; Baiker, A. *Catal. Lett.* **1994**, *26*, 71.
2. Choudhary, V. R.; Uphade, B. S.; Belhekar, A. A. *J. Catal.* **1996**, *163*, 312. (b) Choudhary, V. R.; Banerjee, S.; Uphade, B. S. *Appl. Catal. A: Gen.* **2000**, *197*, L183.
3. (a) Sheldon, R. A.; Kochi, J. K. *Metal-Catalyzed Oxidations of Organic Compounds*, Academic Press: New York, 1981, Chap. 6. (b) Hudlicky, M. *Oxidations in Organic Chemistry*, American Chemical Society: Washington, DC, **1990**. (c) For review: Lenoir, D. *Angew. Chem. Int. Ed.*, **2006**, *45*, 3206.
4. March, J. *Advanced Organic Chemistry: Reactions, Mechanisms, and Structure*, 4th Edn.; John Wiley and Sons: New York, 1992. (b) Cainelli, G.; Cardillon, G. *Chromium Oxidations in Organic Chemistry*, Springer-Verlag: New York, 1984.
5. (a) Barhate, N. B.; Sasidharan, M.; Sudalai, A.; Wakharkar, R. D. *Tetrahedron Lett.* **1996**, *37*, 2067. (b) Bogdal, D.; Lukasiewicz, M. *Synlett* **2000**, 143.
6. Among the various solvents screened for the oxidation of secondary benzylic alcohols in the presence of LaCoO₃ and 70% aq. TBHP, best results were obtained when reaction was carried out in CCl₄. The use of phase transfer catalyst Bu₄N⁺Br⁻ further improved yields of the products.
7. Joseph, R.; Sasidharan, M.; Kumar, R.; Sudalai, A.; Ravindranathan, T. *J. Chem. Soc. Chem. Commun.* **1995**, 1341.
8. A small amount of acetal formation was observed during oxidation of primary alcohols using 90% TBHP and transition metal phthalocyanines as catalyst. Sanderson, J. R.; Marquis, E. T. US Pat. 5,132,465, **1992**.